

The Effect of Cavity Shape and Hybrid Layer on the Stress Distribution of Cervical Composite Restorations

Evrin Eliguzeloglu^a

Oguz Eraslan^b

Huma Omurlu^c

Gurcan Eskitascioglu^d

Sema Belli^e

ABSTRACT

Objectives: The aim of this finite elemental stress analysis study was to evaluate the effect of cavity shape and hybrid layer on the stress distribution of the mandibular premolar tooth under occlusal loading.

Methods: The mandibular premolar tooth was selected as the model based on the anatomical measurements suggested by Wheeler. Four different mathematical models were evaluated: 1) a saucer-shaped non-carious cervical lesion restored with a composite without a hybrid layer, 2) a saucer-shaped non-carious cervical lesion restored with a composite with a hybrid layer, 3) a wedge-shaped non-carious cervical lesion restored with a composite without a hybrid layer, and 4) a wedge-shaped non-carious cervical lesion restored with a composite with a hybrid layer. A 200 N force was applied from the buccal tubercle and central fossa of the premolar tooth. The findings were drawn by the SAPLOT program.

Results: In models 2 and 4, the output showed that a hybrid layer acts as a stress absorber. Additionally, when the cavity shape was changed, the stress distribution was very different.

Conclusions: Cavity shape and hybrid layer play an important role in stress distribution in cervical restorations. (Eur J Dent 2011;5:180-185)

Key words: Non-carious cervical lesion; Hybrid layer; Stress distribution; Finite element analysis; Premolar tooth.

^a Department of Operative Dentistry and Endodontics, Faculty of Dentistry, Yuzuncuyil University, Van, Turkey.

^b Department of Prosthetic Dentistry, Faculty of Dentistry, Selcuk University, Konya, Turkey.

^c Department of Operative Dentistry and Endodontics, Faculty of Dentistry, Gazi University, Ankara, Turkey.

^d Department of Prosthetic Dentistry, Faculty of Dentistry, Yuzuncuyil University, Van, Turkey.

^e Department of Endodontics, Faculty of Dentistry, Selcuk University, Konya, Turkey.

■ Corresponding author: Evrin Eliguzeloglu
Yuzuncuyil University, Faculty of Dentistry
Department of Operative Dentistry and Endodontics,
65080 Van, Turkey.

Phone: +90 505 687 81 37 Fax: +90 312 223 92 26
E-mail: eeliguzeloglu@yahoo.com

INTRODUCTION

Non-carious cervical lesions attributed to erosion, abrasion, and occlusal loading; usually take the shape of a wedge or a saucer.¹⁻³ In wedge-shaped lesions, there is a sharp line angle at the axial wall. In saucer-shaped lesions, is enlarged occlusally relative to the wedge and there is no sharp line.^{4,5} Radenz and colleagues⁶ reported that angular wedge-shaped defects (which are probably related to occlusal loading) were seen more frequently than the rounded variety (which are probably related to erosion) and that defects were seen more commonly on incisors and premolars. A cervical lesion changes the distribution of stress within a tooth. Grippo⁷ suggested that if the lesion were left unrestored, the stress concentration caused by the cervical lesion would facilitate further deterioration of tooth structure. He hypothesized that cervical restoration decreases the concentration of stress and the progression of the lesion.⁷ Therefore, restoration of non-carious cervical lesions is important. Non-carious cervical lesions are restored mostly with resin-based esthetic restorative materials like composite, resin-based glass ionomer.⁸ With composite resin restorations, to obtain proper bonding, forming a hybrid layer in the resin dentin interface is essential.⁹⁻¹¹ In addition, many researchers have asserted that the hybrid zone might act as a stress absorber in the dentin bonding procedures because of its elasticity structure.¹²⁻¹⁵ A hybrid layer is very different from the original tooth structure chemically and physically because it has been partially demineralized and then infiltrated with resin. The resulting structure is neither dentin nor adhesive but a hybrid of the two.¹⁶

The aim of this finite element stress analysis study was to evaluate the effect of hybrid layer on the distribution and the amount of stress formed under occlusal loading in a premolar tooth with wedge-shaped and saucer-shaped cervical lesions, restored with composite. The null hypothesis of this study was that cavity shape and hybrid layer did not affect the stress distribution of the non-carious cervical restorations.

MATERIALS AND METHODS

In this study, a three-dimensional finite element model simulating the cross-section of a

mandibular premolar tooth was used. The mathematical models were based on the anatomical measurements suggested by Wheeler.¹⁷ The model included simulations of cortical bone, spongi-ose bone, periodontal membrane, enamel, dentin, hybrid composite, the adhesive layer, a hybrid layer, and pulp tissue. Their elastic properties, were determined from the literature. The thickness of the composite restorations was 2 mm, the width of the adhesive layer was 30 μm , and the width of the hybrid layer was 1.5 μm .¹⁸ Each mathematical model was composed of 966 nodes and 726 solid elements. The analysis was performed using a computer (Sony Vaio UGN-FZ320EIB 1.66 GHz Intel Core 2 Duo) and the SAP 2000 structural program (Computer Structures Inc. Berkley, CA).

Two different mathematical models including saucer-shaped and wedge-shaped non-carious cervical lesions were created (Figures 1 and 2).

Four different restoration types were evaluated using these models:

Model A: Saucer-shaped non-carious cervical lesion restored with a composite resin without a hybrid layer.

Model B: Saucer-shaped non-carious cervical lesion restored with a composite resin with a hybrid layer.

Model C: Wedge-shaped non-carious cervical lesion restored with a composite resin without a hybrid layer.

Model D: Wedge-shaped non-carious cervical lesion restored with a composite resin with a hybrid layer.

All models were loaded from central fossa and buccal tubercle with a total 200 N force (100 N per each point) (Figures 1 and 2).^{17,19} The final elements on the X and Y axis for each model were assumed to be fixed based on boundary conditions. Stress distribution and amounts have been calculated using von Mises stress criteria.²⁰ The outputs were transferred to the SAPLOT program to display the resulting shear stress values.

RESULTS

Figure 3 (Model A) shows a lower premolar tooth model with a saucer-shaped non-carious cervical lesion restored with a composite resin. In this model, a hybrid layer was not included. When 200 N was loaded on the buccal tubercle and central fossa (100 N for each), more stress accu-

mulation was observed on the gingival margin of the composite restoration. The gingival margin of the composite restoration was seen in yellow (38-46 MPa), and the occlusal margin of the composite was seen in brown (23-31 MPa). When the composite restoration was evaluated mesio-distally, the gingival margin was the most intense surface, and this intensity decreased the occlusal margin of the composite. And when the composite restoration was evaluated bucco-lingually, the stress intensity decreased toward the lingual direction. Figure 4 (Model B) depicts the stress distribution of a lower premolar tooth model with a saucer-shaped non-carious cervical lesion restored with a composite resin. In this model, a hybrid layer was included, and the stress distribution decreased on all composite surfaces (gingival, axial, and occlusal). The gingival margin of the composite restoration was seen in dark yellow (31-38 MPa), and occlusal margin of the composite restoration was seen in red (8-15 MPa) (Figure 4). Figure 5 (Model C) shows a lower premolar tooth model with a wedge-shaped non-carious cervical lesion restored with a composite resin. As with Model A this model did not include a hybrid layer.

The gingival margin of the composite restoration was the most intense surface, seen in light yellow (46-54 MPa), and the occlusal margin of the restoration was seen in brown (23-31 MPa).

Figure 6 (Model D) illustrates the stress distribution of a lower premolar tooth model with a wedge-shaped non-carious cervical lesion restored with a composite resin. This model included a hybrid layer, as did Model B. When a hybrid layer was added, the stress distribution decreased. In this model, the gingival margin of the restoration was seen in dark yellow (31-38 MPa), and occlusal margin of the restoration was seen in brown (23-31 MPa).

DISCUSSION

Non-carious cervical lesions represent a difficult challenge to the dental profession because they are common, because it is likely their prevalence will increase as the nation's population ages, and because the position of these lesions makes it difficult to provide a long-lasting restoration. These lesions were restored with resin-based esthetic restorative materials like composite, resin-based glass ionomer. Researchers report-



Figure 1. A mathematical model including a wedge-shaped non-carious cervical lesion loaded with 200 N is seen.

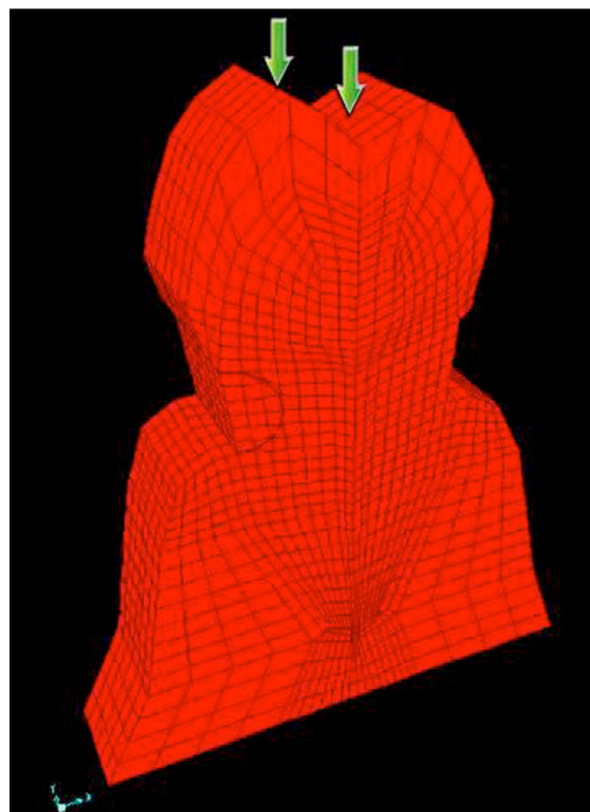


Figure 2. A mathematical model including a saucer-shaped non-carious cervical lesion loaded with 200 N is seen.

ed unfavorable results regarding the longevity of cervical restorations.²¹⁻²⁵ Secondary caries is common around this type of restoration. The ineffectiveness of cervical restorations is caused by the difficulties in bonding sclerotic dentin.^{26,27} In addition to sclerotic dentin; stressful occlusions influence the retentive failure rates. Van Meerbeek et al²⁸ confirmed that stress concentration at the cervical region is responsible for not only the development of cervical lesions, but also restoration retention failure. The stress created by occlusal loadings is not only distributed in structures such as enamel and dentin, but also concentrated in areas such as the composite and adhesive layers.⁴ It was reported that, to reduce this stress, in addition to the utilization of flexible restorative materials, applying flexible adhesives to the resin dentin bonding layer could be beneficial.²⁹ Van Meerbeek et al³⁰ reported that the elastic structure of the hybrid layer formed by collagen tissue and supported by resin can tolerate the stress generated by occlusal loadings. The shaping of hybridization is

the most important mechanism of bonding. During hybridization, the mineral phase of hard tissue is dissolved to expose the collagen matrix, and this matrix is then infiltrated with resin monomer to intentionally change the physical and chemical properties of the hard tissue.³¹

Belli et al¹⁴ analyzed the effect of hybrid layer on the amount and distribution of stress generated by occlusal forces in premolar teeth restored with a composite and ceramic inlay and concluded that the hybrid layer reduced the stress distribution in restorative materials.

Ausiello et al^{12,13} analyzed the effect of hybrid layer in Class II cavities with FEM in two different studies and reported that a hybrid layer served as a cushion to both polymerization shrinking and the stress generated by occlusal forces between restorative material and dental tissue. Different from previous studies, this study analyzed the effect of hybrid layer on the stress distribution of non-carious cervical restorations and determined that it absorbed the stress intensity in the cervical

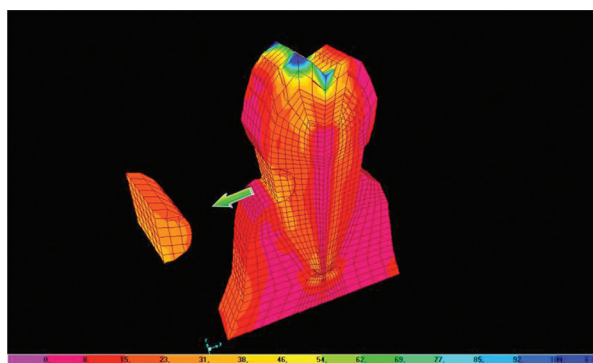


Figure 3. A saucer-shaped non-carious cervical lesion restored with a composite resin without a hybrid layer. When stress distribution was compared, the gingival margin of the composite restoration was the most intense surface [38-46 MPa].

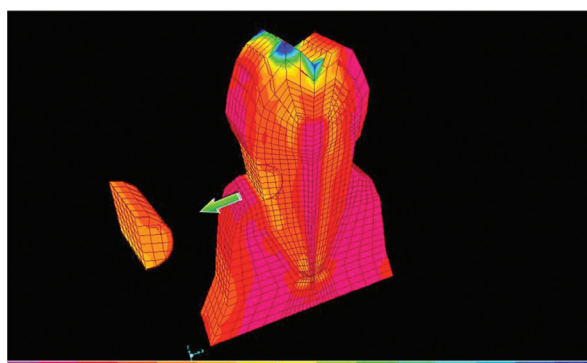


Figure 4. A saucer-shaped non-carious cervical lesion restored with a composite resin with a hybrid layer. When a hybrid layer was added, stress intensity decreased in composite surfaces. The gingival margin of the composite restoration was seen in dark yellow [31-38 MPa].

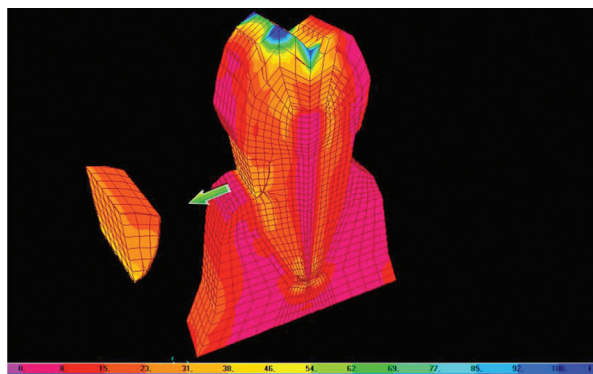


Figure 5. A wedge-shaped non-carious cervical lesion restored with a composite resin without a hybrid layer. The stress distribution was very different from that in saucer-shaped lesions. The gingival margin of the composite restoration was seen in light yellow [46-54 MPa].

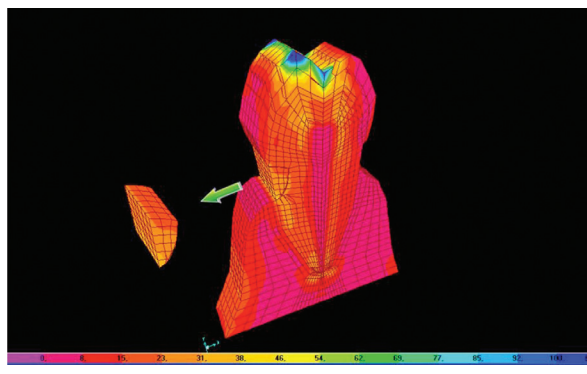


Figure 6. A wedge-shaped non-carious cervical lesion restored with a composite resin with a hybrid layer. The stress intensity decreased in composite surfaces when a hybrid layer was added. The gingival margin of the composite restoration was seen in dark yellow [31-38 MPa].

region induced by occlusal forces. In addition that stress distribution within a mandibular premolar was affected by cavity shape, too. The wedge-shape lesion had a sharp angle at the axial wall. As a result, the stress distribution at the axial wall was higher than in the saucer-shaped lesion. Similar to our results, Kuroe and colleagues⁵ confirmed that differences in lesion shape influenced the interfacial stress between a restoration and tooth structure. From the etiology of cervical abfraction³² or stress induced lesions,³³ a tooth flexure concept is derived that also may affect the retention of Class V adhesive restorations.^{1,24,34,35} The concentration of compressive and tensile stress at the cervical area induced by eccentric or heavy centric occlusal forces may progressively dislodge and eventually debond resin restorations.^{34,35} Elastic buffers underneath composite restorations may also better withstand shocks induced by occlusal loading.²⁹ The results of this study showed that the hybrid layer behaved as an elastic buffer and decreased the stress concentration in the cervical region induced by occlusal forces.

CONCLUSIONS

Within the limitations of this FEM study, the following was concluded:

- The hybrid layer plays an important role in stress distribution. It absorbed the stress created due to the occlusal loading in cervical restorations.
- Cavity shape affected stress distribution in non-carious cervical restorations. The stress distribution of, saucer-shaped non-carious cervical lesions were shown to be more advantageous than wedge-shaped lesions.

REFERENCES

1. Levitch LC, Bader JD, Shugars DA, Heymann HO. Non-carious cervical lesions. *J Dent* 1994;22:195-207.
2. Rees JS, Jagger DC. Abfraction lesions: myth or reality? *J Esthet Restor Dent* 2003;15:263-271.
3. Spranger H. Investigation into the genesis of angular lesions at the cervical margin of teeth. *Quintessence Int* 1995;26:149-154.
4. Gallien GS, Kaplan I, Owens BM. A review of noncarious dental cervical lesion. *Compendium* 1994;15:1366-1374.
5. Kuroe T, Itoh H, Caputo A, Konuma M. Biomechanics of cervical tooth structure lesions and their restoration. *Quintessence Int* 2000;31:267-274.
6. Radentz WH, Barnes GP, Cutright DE. A survey of factors possibly associated with cervical abrasion of tooth surfaces. *J Periodontol* 1976;47:148-154.
7. Grippo JO. Noncarious cervical lesions: The decision to ignore or restore. *J Esthet Dent* 1992;4:55-64.
8. Lee WC, Eakle WS. Stress- induced cervical lesions: review of advances in the past 10 years. *J Prosthet Dent* 1996;75:487-494.
9. Eick JD, Gwinnet AJ, Pashley DH. Current concepts on adhesion to dentin. *Crit Rev Oral Biol Med* 1997;8:306-335.
10. Ferrari M, Goracci G, Garcia- Godoy F. Bonding mechanism of three one bottle systems to conditioned and unconditioned enamel and dentin. *Am J Dent* 1997;10:224-230.
11. Perdigao J, Ramos JC, Lambrechts P. In vitro interfacial relationship between human dentin and one bottle dental adhesives. *Dent Mater* 1997;13:218-227.
12. Ausiello P, Apicella A, Davidson CL. Effect of adhesive layer properties on stress distribution in composite restorations- a 3D finite element analysis. *Dent Mater* 2002;18:295-303.
13. Ausiello P, Apicella A, Davidson CL, Rengo S. 3D finite element analyses of cusp movements in a human upper premolar restored with adhesive resin-based composites. *J Biomech* 2001;34:1269-1277.
14. Belli S, Eskitaşcioğlu G, Eraslan O, Senavongse P, Tagami J. Effect of hybrid layer on stress distribution in a premolar tooth restored with composite or ceramic inlay: an FEM study. *J Biomed Mater Res Part B: Appl Biomater* 2005;74:665-668.
15. Uno S, Finger WJ. Function of the hybrid zone as a stress absorbing layer in resin dentin bonding. *Quintessence Int* 1995;26:733-738.
16. Nakabayashi N, Pashley DH. Hybridization of dental hard tissues. Tokyo: Quintessence Publishing Co, 1998.
17. Ash M, Nelson SJ. Wheeler's dental anatomy, physiology and occlusion. USA, Elsevier, 2003.
18. Eligüzeloglu E, Omurlu H, Eskitaşcioglu G, Belli S. Effect of surface treatments and different adhesives on the hybrid layer thickness of non-carious cervical lesions. *Oper Dent* 2008;33:338-345.
19. Lambrechts P, Braem M, Vanherle G. Buonocore memorial lecture. Evaluation of clinical performance for posterior composite resins and dentin adhesives. *Oper Dent* 1987;12:53-78.
20. Papavassiliou G, Kamposiora P, Bayne SC, Felton DA. 3D FEA of osseointegration percentages and patterns on implant bone interfacial stress. *J Dent* 1997;25:485-491.
21. Bayne SC, Heymann HO, Sturdevant JR, Wilder AD, Sluder TB. Contributing covariables in clinical trials. *Am J Dent* 1991;4:247-250.

22. Browning WD, Brackett WW, Gilpatrick RO. Retention of microfilled and hybrid resin based composite in noncarious class V lesions: a double-blind, randomized clinical trial. *Oper Dent* 1999;24:26-30.
23. Heymann HO, Sturdevant JR., Bayne SC, Wilder AD, Sluder TB, Brunson WD. Examining tooth flexural effects on cervical restorations: a two year clinical study. *JADA* 1991;122:41-47.
24. Heymann HO, Sturdevant JR, Brunson WD, Wilder AD, Sluder TB, Bayne SC. Twelve-month clinical study of dentinal adhesives in class V cervical lesions. *JADA* 1988;116:179-183.
25. Smales RJ, Gerke DC. Clinical evaluation of light-cured anterior resin composites over periods of up to 4 years. *Am J Dent* 1992;5:208-212.
26. Barnes DM, Blank LW, Thompson VP, Holson AM, Gingell JC. A 5 and 8 year clinical evaluation of a posterior composite resin. *Quintessence Int* 1991;22:143-151.
27. Tay FR, Pashley DH. Resin bonding to cervical sclerotic dentin: a review. *J Dent* 2004;32:173-196.
28. van Meerbeek B, Braem M, Lambrechts P, Vanherle G. Evaluation of two dentin adhesives in cervical restorations. *J Prosthet Dent* 1993;70:308-314.
29. Kemp- Schölte CM, Davidson CL. Complete marginal seal of class V resin restorations effected by increased flexibility. *J Dent Res* 1990;69:1240-1243.
30. van Meerbeek B, Williams G, Celis JP, Roos JR, Braem M, Lambrechts P, Vanherle G. Assesment by nano-indentation of the hardness and elasticity of the resin dentin bonding area. *J Dent Res* 1993;72:1434-1442.
31. Nakabayashi N, Kojima K, Masuhara E. The promotion of adhesion by the infiltration of monomers into tooth substrates. *J Biomed Mater Res* 1982;16:265-273.
32. Grippo JO. Abfractions: a new classification of hard tissue lesions of teeth. *J Esthet Dent* 1991;3:15-19.
33. Braem M, Lambrechts P, Vanherle G. Stress induced cervical lesions. *J Prosthet Dent* 1992;67:718-722.
34. Powell LV, Johnson GH, Gordon GE. Factors associated with clinical success of cervical abrasion erosion restorations. *Oper Dent* 1995;20:7-13.
35. van Meerbeek B, Perdigao J, Lambrechts P, Vanherle G. The clinical performance of adhesives. *J Dent* 1998;26:1-20.
36. Menicucci G, Mossolov A, Mozzati M, Lorenzetti M, Preti G. Tooth-implant connection: some biomechanical aspects based on finite element analyses. *Clin Oral Implants Res* 2002;13:334-341.
37. MacGregor AR, Miller TP, Farah JW. Stress analysis of mandibular partial dentures with bounded and free-end saddles. *J Dent* 1980;8:27-34.
38. Reinhardt RA, Pao YC, Krejci RF. Periodontal ligament stresses in the initiation of occlusal traumatism. *J Periodontol Res* 1984;19:238-246.
39. Holmes DC, Loftus JT. Influence of bone quality on stress distribution for endosseous implants. *J Oral Implantol* 1997;23:104-111.