

The effect of surface roughness on ceramics used in dentistry: A review of literature

Haroon Rashid¹

Correspondence: Dr. Haroon Rashid,
Email: drh.rashid@hotmail.com

¹Department of Prosthodontics, Ziauddin College of
Dentistry, Karachi, Pakistan

ABSTRACT

Long term clinical success of modern dental ceramics depends on a number of factors. These factors include the physical properties of the material, the laboratory fabrication process, the laboratory fabrication technique and clinical procedures that may damage these brittle materials. The surface structure and composition of a dental restorative material influences the initial bacterial adhesion, and a rough material surface will accumulate more plaque. Biomaterials for the restoration of oral function are prone to biofilm formation, affecting oral health. An up to date online database search was performed using the keywords “bacterial biofilm,” “ceramic strength,” “dental ceramics” and “surface roughness.” The searches were performed on Medline/PubMed, and Scopus and the cross references were further searched in the databases to verify further studies. The relevant papers included original articles, systemic reviews, case reports and letters to the editor. All the papers were reviewed, and the most relevant studies were selected for referencing by the author. The aim of this paper is to highlight the influence of rougher surfaces on the ceramic strength and plaque accumulation leading to bacterial biofilm formation.

Key words: Bacterial biofilm, ceramics, strength, surface roughness

INTRODUCTION

The interest in aesthetics, biological safety, cost and the efficacy of dental care is becoming greater with time. Porcelain has excellent esthetic properties, and biocompatibility, and major emphasis in research have been directed toward the enhancement of its strength and aesthetic properties. Out of many ceramic restorations, the metal-ceramic ones are still the most commonly used restorations in fixed prosthodontics. Their use is frequent in high-stress bearing areas and in areas where restoration of multiple teeth is required.^[1]

The development of all-ceramic restorative materials has seen many significant changes during the last decade. It is certainly expected that the future will bring more innovative ideas and also will bring fine tuning of the existing ceramics and existing techniques.^[2] Due to the unsurpassed mechanical properties of Zirconia, its introduction to the dental

market, almost a decade ago, there was considerable expansion in the range of applications of ceramics in dentistry, a field where they are classically in demand due to their chemical inertness and a wide combination of optical properties, allowing excellent esthetics. Common ceramic materials currently in dental use and their clinical recommendations are enlisted in Table 1.

Zirconia (ZrO_2) is a ceramic material with excellent mechanical properties with a compression resistance of about 2000 MPa. When stabilized with Y_2O_3 , it offers the best properties for dental applications. Whenever a stress occurs on zirconia surface, a crystalline modification occurs which opposes the propagation of cracks. With fracture toughness twice or more that of alumina ceramics, transformation toughened zirconia represents an exciting potential substructure material. The invention of other all-ceramic systems like Techceram (Techceram Ltd, Shipley, UK), or any of the large number of computer-aided design/computer-aided manufacturing (CAD-CAM) systems

How to cite this article: Rashid H. The effect of surface roughness on ceramics used in dentistry: A review of literature. Eur J Dent 2014;8:571-9.

Copyright © 2014 Dental Investigations Society.

DOI: 10.4103/1305-7456.143646

Table 1: List of all-ceramic materials, commonly used in dentistry

Material name	Material type	Laboratory fabrication technique/procedure	Clinical recommendations
Vitablocs Mark II	Feldspathic ceramic	CAD/CAM	Inlays, onlays, veneers, anterior and posterior crowns
Cerec	Feldspathic ceramic	CAD/CAM	Inlays, onlays, veneers, anterior and posterior crowns
Techceram	Aluminous ceramic	Flame spraying	Inlays, anterior and posterior crowns
IPS Empress	Leucite re-enforced glass-ceramic	Pressable	Inlays, onlays, veneers, anterior crowns
IPS Empress CAD/CAM	Leucite re-enforced glass-ceramic	CAD/CAM	Inlays, onlays, veneers, anterior and posterior crowns
IPS E.Max	Lithium disilicate glass-ceramic	Pressable	Inlays, onlays, veneers, anterior and posterior crowns
IPS E.Max CAD/CAM	Lithium disilicate glass-ceramic	CAD/CAM	Inlays, onlays, veneers, anterior and posterior crowns, anterior fixed partial dentures
In-ceram Alumina	Glass infiltrated alumina	CAD/CAM	Onlays, anterior and posterior crowns, anterior fixed partial dentures
In-ceram Zirconia	Glass infiltrated alumina (ZrO added)	CAD/CAM	Onlays, posterior crowns and posterior fixed partial dentures
Procera	Polycrystalline alumina	CAD/CAM	Anterior and posterior crowns
Lava Zirconia	Polycrystalline zirconia (Y-TZP)	CAD/CAM	Anterior crowns, posterior crowns, anterior and posterior fixed partial dentures

CAD: Computer-aided design, CAM: Computer-aided manufacturing

e.g. Cerec (Siemens, Bensheim, Germany) and Procera (Nobel Biocare, Goteberg, Sweden) shows that there is an increased demand of tooth colored metal free restorations and that will certainly lead to further decrease in use of traditional cast metals used in fabrication of restorations.^[3,4] Techceram all-ceramic crowns rely on a base layer that is manufactured by a 'flame spraying' specialist grade alumina powder onto a refractory model before sintering. The base layer is usually 0.5 mm thick for crowns and can be translucent or colored. This system is suitable for anterior and posterior single crowns and inlays and has a biaxial flexural strength of 300 Mpa. Procera, consists of high strength alumina core that is veneered using traditional porcelain. Uniform Procera copings of 0.4-0.6 mm are milled and sintered at 1600° before traditional porcelain can be added for anterior and posterior restorations. Cerec materials are available in a wide variety of shades and translucencies offering strength of 140 MPa. It has been in the market for more than 2 decades and has been routinely used to fabricate restorations including inlays, onlays, single crowns (anterior and posterior) and veneers.

Porcelain is essentially a white, translucent ceramic that is fired to a glazed state.^[5] It is classified by its microstructure, processing technique and by the firing temperature. According to the firing temperature, porcelain is of ultra-low fusing, low fusing, medium fusing and high fusing type. The firing temperature ranges of dental porcelain and the clinical recommendations are enumerated in Table 2. Roughness of the porcelain can be due to certain laboratory or production reasons but may also

Table 2: Firing temperature ranges of dental porcelain and their applications

Porcelain type	Firing temperature range	Clinical recommendations
High fusing	>1300°	Denture teeth, sintered alumina and zirconia core ceramics
Medium fusing	1000°-1300°	Denture teeth, presintered zirconia
Low fusing	850°-1000°	Crown and bridge veneer ceramic
Ultra low fusing	<850°	Crown and bridge veneer ceramic

result from chair-side modifications of the finished restoration. Finished porcelain restorations from the technical laboratory ideally should not require any changes when fitted to the patient's mouth. However, it is often necessary to adjust the occlusion for the comfort of the patient. These adjustments will then require chair side polishing to reduce the incidence of porcelain fracture, opposing tooth wear and bacterial accumulation.^[6] The roughness of the intra-oral surfaces has a major impact on the initial adhesion and the retention of microorganisms, and if the roughness were sub-gingival, the retention of the microorganisms would be more.^[7,8] The oral cavity is constantly contaminated by a complex diversity of microbial species that have a strong tendency to colonize surfaces. The major components involved in biofilm formation are bacterial cells, a solid surface, and a fluid medium.^[9,10]

Skills of the clinician and technician are important for the long-term success of a restoration. The success is also dependent on the strength of the material, its solubility in acids and the thermal its stability.^[11]

FINISHING AND POLISHING OF CERAMIC RESTORATIONS

A laboratory finished ceramic restoration ideally should retain the surface glaze after it has been fitted to the abutment teeth in the oral cavity.^[12,13] However, this is not always the case, and there are scenarios where adjustments are required on them. These adjustments and modifications are necessary to correct occlusal interferences and for improvements in aesthetics. A rough surface [Figure 1] will abrade the opposing dentition or restoration, and it is highly recommended that the adjusted surface is finished and polished appropriately.

Martínez-Gomis *et al.*,^[14] used four different polishing techniques on a ceramic surface. Sof-lex discs white silicon, shofu polishing kit and diamond burs were used, and Sof-lex discs provided the smoothest surface finish. Odatsu *et al.*,^[15] used carborundum points, silicone points and diamond polishing paste on zirconia and traditional feldspathic porcelain. Feldspathic porcelain showed highest surface roughness values after finishing and polishing procedures.

The use of diamond polishing pastes for porcelain polishing in the dental office is a common practice in dentistry.^[16,17] These pastes provide efficient polishing, and their use can be recommended with an appropriate vehicle. Polishing brushes, rubber cups, polishing brushes combined with abrasive pastes on tooth are the most commonly used procedures clinically.^[18]

Loss of surface glaze is the usual result of the clinical intra-oral adjustment process, a situation that must be corrected by re-glazing or polishing to obtain clinical success. Surface treatments affect surface roughness and color stability, and adjusted/polished restorations could also be susceptible to staining.^[19] Stainability is another important factor in the long-term clinical success of ceramic restorations. Contour adjustments on restoration surfaces cause differences in ceramic texture that may be affected differently by the staining agent. The use of appropriate polishing materials with a compatible porcelain may reduce stainability.^[20,21]

THE EFFECT OF SURFACE GLAZE

Glazing of ceramic restorations is a routine laboratory procedure which involves the provision of aesthetic

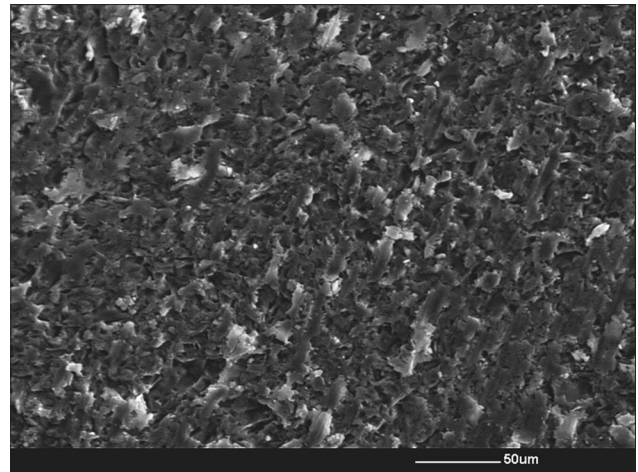


Figure 1: Scanning electron microscopy image of a rough ceramic surface roughened using a diamond instrument

and hygienic glass coated surfaces to the finished restorations.^[22] It is said that glazing is done to strengthen the restoration, but this is uncertain. Binns^[23] stated that the process of glazing is a way of strengthening glass. However, he also has questioned the efficacy of this procedure as the surface of a dental porcelain appliance is often ground subsequent to glazing in the dental office and still provides reasonable clinical service.

The procedure of self-glazing is appropriate for the clinical use as this will provide the restoration with a smooth, hygienic surface with specimens showing better color stability.^[24] Glazing as the means for strengthening brittle glass can be considered as the production of a surface layer of a thermal expansion which is lower.^[25] This will serve two functions that are, it will place the surface into a compressive state, and it will also reduce the depth and width of surface flaws and will strengthen the material theoretically. However, it may be that the strength of dental porcelain is controlled by intrinsic factors rather than the surface flaws.^[26]

Manipulation of porcelain requires adequate skills of laboratory technicians and fabricating porcelain crowns and bridges is highly technique sensitive. Minor laboratory faults may result in clinically unacceptable surface layers. One of the major faults as described by Rashid^[27] is the formation of porosities. These porosities [Figure 2] may in turn affect the surface roughness, texture and shade. Common reasons for the formation of porosities in dental porcelain are faults during condensation, in-appropriate powder/liquid mixing ratio and due to variations in firing time and temperature.^[28-30]

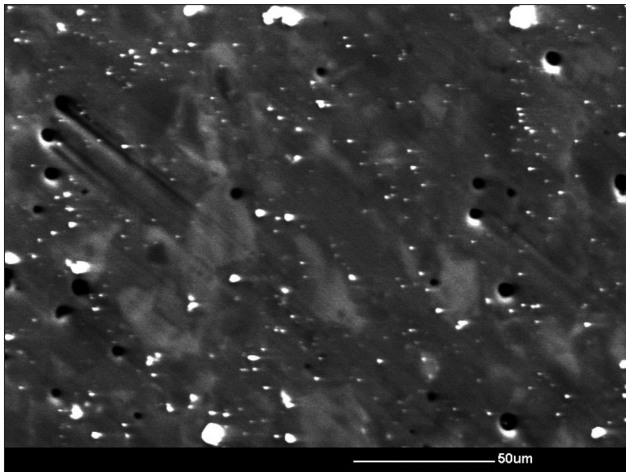


Figure 2: Scanning electron microscopy image of a glazed ceramic surface showing numerous porosities

STRENGTH AND SURFACE ROUGHNESS

The shape, sharpness, size, the depth of the surface flaws and internal defects determines the strength of the material.^[31,32] Various techniques of polishing porcelain and glazing have been proposed to strengthen the material after the introduction of surface flaws, but it is still not clear if these measures are effective. Haralur^[22] conducted a study on Vita VMK porcelain and evaluated the efficacy of Shofu polishing kit. Their results indicated that glazed surfaces showed the lowest values for surface roughness. However, Rashid^[27] concluded in their study that VITA VMK glazed porcelain surfaces were rougher as compared to polished surfaces. However, both authors used different polishing techniques but used similar porcelain specimens in their investigations. Martínez-Gomis *et al.*^[14] used different polishing techniques on a ceramic after its roughening using a diamond instrument/bur. Their investigation included the use of white polishing discs, Shofu discs and Sof-lex discs. Their results showed that Sof-lex discs produced the best finishes. Al-Shammery *et al.*^[6] also concluded that Sof-lex discs produce best finishes on a CAD/CAM ceramic but in their study, the control group did not include glazed specimens but instead included roughened specimens. The fact that different polishing techniques may produce different results can also be explained by the fact that different systems for surface roughness evaluation have been used in different studies. The evaluating equipment included the use of scanning electron microscopy (SEM), perthometer, a tactile profilometry and confocal microscopy. These systems have different accuracies of measurements and thus may produce different results.

The strength of a porcelain material was largely determined by its surface roughness and the inner structure of the material may cause a larger stress concentration than that caused by the surface roughness in combination with the surface flaws present on the material.^[33] If the material is given an adequate surface treatment, it will not require properties that stop cracking and the surface of the material would remain smooth, which in turn results in a restoration that will be long lasting.

Clinically, common problems with ceramic materials in the literature are chipping, marginal fracture and fracture of the restoration bulk.^[34,35] Bulk fractures are still one of the main reason for failures, but reports have also suggested long term survival of different ceramic systems.^[36-38] These fractures are observed throughout their clinical life. Prospective studies on zirconia ceramics have shown to give promising long time results, but authors also reported 15% chipping of the veneering ceramics.^[39-42] High demands of aesthetic and biocompatible materials extend the significance of ceramics in dentistry and main emphasis of the developers around the world has been towards the improvement of the mechanical properties.

In general, ceramic strength is limited by the size and distribution of an inherent flaw population. Fracture may occur without measurable plastic deformation and failure can also start from small flaws prior to plastic deformation. This fact is expressed by a low resistance against crack extension, which is characterized by the parameter fracture toughness K_{Ic} .^[43] Combination of bending and torsion forces produce surface flaws in ceramics and once critical dimensions are reached, the fracture occurs. Numerous studies have shown that catastrophic failure may occur far below the short-time fracture strength due to a slow growth of a subcritical crack up to the critical crack length.^[44,45] This indicates that the strength degradation is measured during a period of a lifetime.^[46] Slow crack growth is strongly influenced by the amount and composition of a glass phase in the ceramic microstructure^[47] and the deleterious effect of slow crack propagation may be attributed to the stress-enhanced chemical reaction occurring in the presence of water vapor at a crack tip. This occurs preferentially in silicate base glasses resulting in bond rupture.^[48] Studies indicate that even moisture levels of 0.017% may cause stress corrosion.^[49] Charles^[50] explained that cracks present in ceramics tend to grow at a slow rate first under the influence of stress. This slow growth of cracks

continues until the intensity of stress reaches a critical value for a particular ceramic restorative material.

Several factors including powder compaction, process of forming, firing and also shaping can also cause flaws in ceramics. During these laboratory processes, the flaws may become inherited in the micro structure of the ceramic. Damage caused during grinding; pull-out caused during polishing, micro-porosity present on the subsurface and the introduction of large pores by technicians during restoration manufacture are common technical laboratory flaws.^[20,51] Other flaws may be inherent which include cracking around grains with thermal expansion and porosities, which are developed during the process of ceramic firing.^[52]

The failure of many materials, including ceramics, is attributed to the propagation of densely distributed cracks, rather than to a single precisely defined the fracture.^[53] The number of cracks and micro cracks is extremely large, and their location and orientation are random. Irwin^[54] demonstrated that stress intensity is related to a crack shape in a particular location with respect to the loading geometry. The finishing procedures influence the existence of micro cracks and residual stress. For example, glazing could round the crack tip of possible micro crack and these changes in length and tip would in turn change the strength of the material. Surface roughness will lead to a non-uniform stress distribution and concentrate locally an applied stress due to the shape differences in the surface layer.^[33] Due to the presence of surface roughness, the developed cracks may not propagate randomly, but occur or propagate at points with higher stress. The theory that initiation of cracks starts at stress concentration points caused by surface roughness was given by Mecholsky *et al.*^[55] who loaded samples with grinding grooves and gouges both perpendicular and parallel to the loading direction.

Since fabrication of conventional dental porcelains consists of a frit condensation, followed by a sintering process, thermally induced residual stresses in the material may also be introduced^[56] which may cause modification of the measured biaxial flexure strength.^[57-59] The moisture content of the veneering material during sintering might induce changes in the zirconia/veneering interface and provoke transformation from the tetragonal phase to the monoclinic phase.^[60] Swain *et al.*^[61] recognized that residual stresses and contact-induced cracking will develop chip-fracture. Beuer *et al.*^[62] reported higher strength of CAD/CAM veneering ceramic compared

to the layered veneering technique. Using of the pressed ceramic may reduce the chipping incidence,^[63] since the heat pressing fabrication method would reduce the formation of large surface and flaws present in the bulk of the material. This would minimize the thermally induced residual^[56,59] stresses. Greater porosities are results of human error that may occur during the fabrication stages in the dental laboratory.^[64,65] The shrinkage level of the porcelain may be related to the ratio of the mixed powder/liquid veneering ceramic and minimal three firing cycles are required. Catastrophic failures may also be induced by the incorporation of small impurities like pores, since cracks cannot be healed, but slow growth may occur under oral conditions.^[65-67]

BACTERIAL ADHESION AND BIOFILM FORMATION

The oral cavity is an open growth system.^[7] Various organisms are present in the oral cavity, and they are considered to be responsible for tooth decay and infections of the oral cavity.^[68] Usually, the survival of the organisms is easy when they adhere to rough surfaces in the mouth.^[7,8] The roughness of intra oral surfaces has a major impact on the initial adherence and the retention of micro-organisms, and if the roughness were sub-gingival, the retention of the micro-organisms would be more.^[7] SEM clearly revealed that the initial adherence and colonization on the tooth enamel started where surface irregularities were present. These surface irregularities, include cracks, grooves and abrasion defects. The colonization of bacteria then spreads out from these irregularities to other areas of teeth. Surfaces in the oral cavity such as the dorsum of the tongue roughened by presence of papilla and the desquamating epithelium of the mucosa harbors other surfaces for the adhesion of bacteria. Along with these surfaces, the enamel surface of gingival crevices and the tonsils are also believed to be the sites where bacterial adhesion occurs. Microorganisms as stated by the authors are specifically present at these sites, but they are believed to exist on all the hard and soft tissues of the oral cavity. The rough surfaces may also cause aesthetic problems at the facial surfaces. Furthermore, a rough occlusal surface is also not acceptable clinically.^[6] The increase in surface roughness on fabricated ceramic restorations may result from chair-side modifications of the restoration by the clinician. These modifications are sometimes necessary for proper contouring of

the restoration which includes the reduction of the proximal contour, to provide inter-proximal contact areas, adjusting the occlusal contacts and the refining of the cervical margins.

Biofilms are believed to be formed on nearly all surfaces exposed to the natural environment.^[69] There is no doubt that the biofilm formation in the mouth is a well-known example and controlling its formation is an everlasting daily struggle for the researchers and for all of us. Biofilms forms on all dental hard and soft tissues and is the major cause of caries and periodontal problems.^[70] It also affects the biomaterial surfaces used for the restoration of function in the oral cavity. Although, initially, the biofilm formation on biomaterial surfaces in the mouth could appear fairly harmless, dependent on its site, its consequences may be much more harmful and severe. Similar to the development of periodontitis after accumulation around the gingiva, biofilms around dental implants may lead to their infection that is, peri-implantitis.^[71] A Class II filling which is overhanging and is located in the gingival margin is prone to bacterial colonization, with an impact on gingival health.^[72-74] The surfaces of composite resins get roughened due to biofilm formation leading to their degradation.^[75] The colonizing bacteria over composites, usually, invade the interface between the restoration and the tooth,^[76] leading to secondary caries^[77] and pulpal pathology.^[78] Around the brackets during orthodontic treatment, biofilms may cause demineralization of the surrounding enamel leading to a negative side-effect of the treatment.^[79,80] Consequently, the interest in new dental materials attracting less biofilm or releasing antimicrobial compounds is increasing.

Four well-defined stages of biofilm formation in the oral cavity have been described in the literature.^[81-86] These are:

Stage 1: Surface transport

Brownian motion causes the initial transport of a bacterium to the surface, through sedimentation of the bacterium in the solution, through liquid flow or through active bacterial movement. Microbial aggregates may also lead to microbial transportation.

Stage 2: Initial adherence phase

This is the stage where reversible adhesion of the bacterium occurs through long-and short-range forces. The organisms will be attracted or repelled by the surface, depending on the result of non-specific interaction forces.

Stage 3: Attachment phase

Once the contact is established between bacterium and surface, a firm anchorage between bacteria and surface is established by specific interactions that are, covalent, ionic or hydrogen bonding.

Stage 4: Plaque maturation phase

When the firmly attached microorganisms start growing and newly formed cells remain attached, biofilms can develop. The growth rate of sessile microorganisms has been found to be partially depending on the biomaterial involved.

Teughels *et al.*^[87] conducted a Medline search and summarized the data of 24 papers as follows:

- Rougher surfaces of crowns, bridges, implant abutments, and denture bases accumulate and retain more plaque
- After several days of undisturbed plaque formation, rough surfaces harbor a more mature plaque characterized by an increased proportion of rods, motile organisms, and spirochetes
- Tooth surfaces with rough surfaces are more frequently surrounded by an inflamed periodontium, characterized by a higher bleeding index, an increased crevicular fluid production, and/or an increased inflammatory infiltrate.

It may be well-known that less plaque accumulates on ceramic or porcelain restorations; a rough surface accelerates plaque accumulation.^[88] Increased amount of plaque on the rough surfaces of ceramics will exert not only caries-causing virulence, but also a harmful influence on periodontal tissue. For a full-coverage crown or a bridge, caries incidence risk would be slight, but instead much attention has to be given to the gingival tissues. Kawai *et al.*^[88] concluded that more plaque was adhered over glazed surfaces of ceramics as compared with their polished surfaces. This means that a glazed surface would not be clinically acceptable from a biologic point of view. Glazing can produce an undulating and rough surface that, usually, has irregularities, inducing more adhesion of bacteria and other substances. Rashid^[27] also concluded that glazed surfaces are rougher as compared to the polished surfaces. Although polished surfaces have been reported to have voids and micro cracks on the subsurface of porcelain,^[89] these superficial defects did not contribute to the Average Roughness (Ra) values or the amount of plaque adhesion. Contrary to other reports, polishing with diamond paste is helpful for obtaining a smoother surface that will prevent plaque from accumulating.

Hahn *et al.*^[90] mentioned that the inlays of two ceramic types collected less plaque with reduced viability over a three-day period of no oral hygiene than did the natural tooth surface. Auschill^[91] showed that biofilms on ceramic biomaterials formed *in vivo* during 5 days were relatively thin, but highly viable. They suggested that thick biofilms are less viable than thin ones, due to a hampered supply of nutrients to a thick biofilm. The effect of surface glazing and polishing of ceramics on early dental biofilm formation was evaluated and found that glazed surfaces tended to accumulate more biofilm compared to polished surfaces.^[92] However, Bremer *et al.*^[93] mentioned that Biofilm formation on various types of dental ceramics differed significantly; and found zirconia to exhibit low plaque accumulation.

CONCLUSION

Ceramic failure is largely influenced by the presence of densely distributed cracks present on rougher surfaces. Modification of surface finishing of ceramics influences their strength and may cause weakening of the structure. If occlusal grinding of a ceramic restoration is done after its cementation, there is always a need for careful intra-oral polishing. If adequate polishing is not done, there is also a tendency that micro-cracks are left which may cause catastrophic fractures in the future. The surface quality of dental ceramics also influences the formation of bacterial biofilm. In the oral environment, the dental plaque forms a constant threat for periodontitis and other conditions such as peri-implantitis, in susceptible individuals. The adherence of microbial species to dental ceramics and the subsequent formation of biofilms on their rough surfaces may also be contributory factors to plaque-related systemic diseases.

REFERENCES

- Moffa JP. Porcelain materials. *Adv Dent Res* 1988;2:3-6, 8.
- Kelly JR, Benetti P. Ceramic materials in dentistry: Historical evolution and current practice. *Aust Dent J* 2011;56 Suppl 1:84-96.
- Shenoy A, Shenoy N. Dental ceramics: An update. *J Conserv Dent* 2010;13:195-203.
- Qualtrough AJ, Piddock V. Dental ceramics: what's new? *Dent Update* 2002;29:25-33.
- Brien O. *Dental Materials and Their Selection*. 3rd ed., Ch. 15. Chicago: Quintessence; 2002. p. 210-6.
- Al-Shammery HA, Bubbs NL, Youngson CC, Fasbinder DJ, Wood DJ. The use of confocal microscopy to assess surface roughness of two milled CAD-CAM ceramics following two polishing techniques. *Dent Mater* 2007;23:736-41.
- Quirynen M, Bollen CM. The influence of surface roughness and surface-free energy on supra- and subgingival plaque formation in man. A review of the literature. *J Clin Periodontol* 1995;22:1-14.
- Quirynen M, Marechal M, Busscher HJ, Weerkamp AH, Darius PL, van Steenberghe D. The influence of surface free energy and surface roughness on early plaque formation. An *in vivo* study in man. *J Clin Periodontol* 1990;17:138-44.
- Gharechahi M, Moosavi H, Forghani M. Effect of surface roughness and materials composition on biofilm formation. *J Biomater Nanobiotechnol* 2012;3:541-6.
- Busscher HJ, Rinastiti M, Siswomihardjo W, van der Mei HC. Biofilm formation on dental restorative and implant materials. *J Dent Res* 2010;89:657-65.
- Isgro G, Kleverlaan CJ, Wang H, Feilzer AJ. The influence of multiple firing on thermal contraction of ceramic materials used for the fabrication of layered all-ceramic dental restorations. *Dent Mater* 2005;21:557-64.
- Boaventura JM, Nishida R, Elossais AA, Lima DM, Reis JM, Campos EA, *et al.* Effect finishing and polishing procedures on the surface roughness of IPS Empress 2 ceramic. *Acta Odontol Scand* 2013;71:438-43.
- Flury S, Lussi A, Zimmerli B. Performance of different polishing techniques for direct CAD/CAM ceramic restorations. *Oper Dent* 2010;35:470-81.
- Martinez-Gomis J, Bizar J, Anglada JM, Samsó J, Peraire M. Comparative evaluation of four finishing systems on one ceramic surface. *Int J Prosthodont* 2003;16:74-7.
- Odatsu T, Jimbo R, Wennerberg A, Watanabe I, Sawase T. Effect of polishing and finishing procedures on the surface integrity of restorative ceramics. *Am J Dent* 2013;26:51-5.
- Haywood VB, Heymann HO, Kusy RP, Whitley JQ, Andreas SB. Polishing porcelain veneers: An SEM and specular reflectance analysis. *Dent Mater* 1988;4:116-21.
- Camacho GB, Vinha D, Panzeri H, Nonaka T, Gonçalves M. Surface roughness of a dental ceramic after polishing with different vehicles and diamond pastes. *Braz Dent J* 2006;17:191-4.
- Sarikaya I, Güler AU. Effects of different polishing techniques on the surface roughness of dental porcelains. *J Appl Oral Sci* 2010;18:10-6.
- Motro PF, Kursoglu P, Kazazoglu E. Effects of different surface treatments on stainability of ceramics. *J Prosthet Dent* 2012;108:231-7.
- Kursoglu P, Karagoz Motro PF, Kazazoglu E. Correlation of surface texture with the stainability of ceramics. *J Prosthet Dent* 2014;112:306-13.
- Sethi S, Kakade D, Jambhekar S, Jain V. An *in vitro* investigation to compare the surface roughness of auto glazed, reglazed and chair side polished surfaces of Ivoclar and Vita feldspathic porcelain. *J Indian Prosthodont Soc* 2013;13:478-85.
- Haralur SB. Evaluation of efficiency of manual polishing over autoglazed and overglazed porcelain and its effect on plaque accumulation. *J Adv Prosthodont* 2012;4:179-86.
- Binns D. The physical and chemical properties of dental porcelain (41-48). In: McLean JW, editor. *Dental Ceramics*. Proceeding of the First International Symposium on Ceramics. Chicago, USA: Quintessence Publishing; 1983.
- Yilmaz C, Korkmaz T, Demirköprülü H, Ergün G, Ozkan Y. Color stability of glazed and polished dental porcelains. *J Prosthodont* 2008;17:20-4.
- Fairhurst CW, Lockwood PE, Ringle RD, Thompson WO. The effect of glaze on porcelain strength. *Dent Mater* 1992;8:203-7.
- Corbitt G, Morena R, Fairhurst C. Fracture stress of a commercial dental porcelain and its components. *J Dent Res* 1985;64:296.
- Rashid H. Comparing glazed and polished ceramic surfaces using confocal laser scanning microscopy. *J Adv Microscop Res* 2012;7:208-13.
- Evans DB, Barghi N, Malloy CM, Windeler AS. The influence of condensation method on porosity and shade of body porcelain. *J Prosthet Dent* 1990;63:380-9.
- Zhang Y, Griggs JA, Benham AW. Influence of powder/liquid mixing ratio on porosity and translucency of dental porcelains. *J Prosthet Dent* 2004;91:128-35.
- Cheung KC, Darvell BW. Sintering of dental porcelain: effect of time and temperature on appearance and porosity. *Dent Mater* 2002;18:163-73.
- Mencik J. *Strength and Fracture of Glass Ceramics*. Glass Science and Technology. Vol. 12. Amsterdam: Elsevier; 1992.
- Fischer H, Schäfer M, Marx R. Effect of surface roughness on flexural strength of veneer ceramics. *J Dent Res* 2003;82:972-5.
- de Jager N, Feilzer AJ, Davidson CL. The influence of surface

- roughness on porcelain strength. *Dent Mater* 2000;16:381-8.
34. Molin MK, Karlsson SL. A randomized 5-year clinical evaluation of 3 ceramic inlay systems. *Int J Prosthodont* 2000;13:194-200.
 35. Krämer N, Frankenberger R. Clinical performance of bonded leucite-reinforced glass ceramic inlays and onlays after eight years. *Dent Mater* 2005;21:262-71.
 36. Pallesen U, van Dijken JW. An 8-year evaluation of sintered ceramic and glass ceramic inlays processed by the Cerec CAD/CAM system. *Eur J Oral Sci* 2000;108:239-46.
 37. Hayashi M, Wilson NH, Yeung CA, Worthington HV. Systematic review of ceramic inlays. *Clin Oral Investig* 2003;7:8-19.
 38. Reiss B, Walther W. Clinical long-term results and 10-year Kaplan-Meier analysis of Cerec restorations. *Int J Comput Dent* 2000;3:9-23.
 39. Raigrodski AJ, Chiche GJ, Potiket N, Hochstedler JL, Mohamed SE, Billiot S, *et al.* The efficacy of posterior three-unit zirconium-oxide-based ceramic fixed partial dental prostheses: A prospective clinical pilot study. *J Prosthet Dent* 2006;96:237-44.
 40. Sailer I, Fehér A, Filser F, Gauckler LJ, Lüthy H, Hämmerle CH. Five-year clinical results of zirconia frameworks for posterior fixed partial dentures. *Int J Prosthodont* 2007;20:383-8.
 41. Tinschert J, Schulze KA, Natt G, Latzke P, Heussen N, Spiekermann H. Clinical behavior of zirconia-based fixed partial dentures made of DC-Zirkon: 3-year results. *Int J Prosthodont* 2008;21:217-22.
 42. Beuer F, Edelhoff D, Gernet W, Sorensen JA. Three-year clinical prospective evaluation of zirconia-based posterior fixed dental prostheses (FDPs). *Clin Oral Investig* 2009;13:445-51.
 43. Munz D, Fett T. *Ceramics*. Berlin: Springer; 1999.
 44. Fairhurst CW, Lockwood PE, Ringle RD, Twigg SW. Dynamic fatigue of feldspathic porcelain. *Dent Mater* 1993;9:269-73.
 45. Ritchie R, Dauskardt R. Cyclic fatigue of ceramics: A mechanics approach to subcritical crack growth and life prediction. *J Ceram Soc Japan* 1991;99:1047-62.
 46. Mecholsky JJ Jr. Fracture mechanics principles. *Dent Mater* 1995;11:111-2.
 47. Bloyer DR, McNaney JM, Cannon RM, Saiz E, Tomsia AP, Ritchie RO. Stress-corrosion crack growth of Si-Na-K-Mg-Ca-P-O bioactive glasses in simulated human physiological environment. *Biomaterials* 2007;28:4901-11.
 48. Charles R. Dynamic fatigue of glass. *J Appl Phys* 1958;29:1657-62.
 49. Wiederhorn S. Influence of water vapor on crack propagation in soda-lime-glass. *J Am Ceram Soc* 1967;50:407-14.
 50. Charles R. Static fatigue of glass. *J Appl Phys* 1958;29:1549-53.
 51. Dalkiz M, Sipahi C, Beydemir B. Effects of six surface treatment methods on the surface roughness of a low-fusing and an ultra low-fusing feldspathic ceramic material. *J Prosthodont* 2009;18:217-22.
 52. Kelly JR, Tesk JA, Sorensen JA. Failure of all-ceramic fixed partial dentures *in vitro* and *in vivo*: Analysis and modeling. *J Dent Res* 1995;74:1253-8.
 53. Bazant Z. Mechanics of distributed cracking. *Appl Mech Rev* 1986;39:675-705.
 54. Irwin G. Analysis of stresses and strains near the end of a crack transversing a plate. *J Appl Mech* 1957;24:361-4.
 55. Mecholsky J, Freiman S, Rice R. Effect of grinding on flaw geometry and fracture of glass. *J Am Ceram Soc* 1977;60:114-7.
 56. Coffey JP, Anusavice KJ, DeHoff PH, Lee RB, Hojjatie B. Influence of contraction mismatch and cooling rate on flexural failure of PFM systems. *J Dent Res* 1988;67:61-5.
 57. Isgró G, Addison O, Fleming GJ. Transient and residual stresses induced during the sintering of two dentin ceramics. *Dent Mater* 2011;27:379-85.
 58. McLean JW, Hughes TH. The reinforcement of dental porcelain with ceramic oxides. *Br Dent J* 1965 21;119:251-67.
 59. Isgró G, Addison O, Fleming GJ. Transient and residual stresses in a pressable glass-ceramic before and after resin-cement coating determined using profilometry. *J Dent* 2011;39:368-75.
 60. Tholey MJ, Swain MV, Thiel N. SEM observations of porcelain Y-TZP interface. *Dent Mater* 2009;25:857-62.
 61. Swain MV. Unstable cracking (chipping) of veneering porcelain on all-ceramic dental crowns and fixed partial dentures. *Acta Biomater* 2009;5:1668-77.
 62. Beuer F, Schweiger J, Eichberger M, Kappert HF, Gernet W, Edelhoff D. High-strength CAD/CAM-fabricated veneering material sintered to zirconia copings – A new fabrication mode for all-ceramic restorations. *Dent Mater* 2009;25:121-8.
 63. Schley JS, Heussen N, Reich S, Fischer J, Haselhuhn K, Wolfart S. Survival probability of zirconia-based fixed dental prostheses up to 5 yr: A systematic review of the literature. *Eur J Oral Sci* 2010;118:443-50.
 64. Albashaireh ZS, Ghazal M, Kern M. Two-body wear of different ceramic materials opposed to zirconia ceramic. *J Prosthet Dent* 2010;104:105-13.
 65. Stawarczyk B, Ozcan M, Roos M, Trottmann A, Sailer I, Hämmerle CH. Load-bearing capacity and failure types of anterior zirconia crowns veneered with overpressing and layering techniques. *Dent Mater* 2011;27:1045-53.
 66. Drummond JL. Ceramic behavior under different environmental and loading conditions. *Dental Materials in vivo: Aging and Related Phenomena*. IL: Quinte Chicago; 2003. p. 35-45.
 67. Holden JE, Goldstein GR, Hittelman EL, Clark EA. Comparison of the marginal fit of pressable ceramic to metal ceramic restorations. *J Prosthodont* 2009;18:645-8.
 68. Loesche WJ, Syed SA, Schmidt E, Morrison EC. Bacterial profiles of subgingival plaques in periodontitis. *J Periodontol* 1985;56:447-56.
 69. Moons P, Michiels CW, Aertsen A. Bacterial interactions in biofilms. *Crit Rev Microbiol* 2009;35:157-68.
 70. Sbordone L, Bortolaia C. Oral microbial biofilms and plaque-related diseases: microbial communities and their role in the shift from oral health to disease. *Clin Oral Invest* 2003;7:181-8.
 71. Grössner-Schreiber B, Teichmann J, Hannig M, Dörfer C, Wenderoth DF, Ott SJ. Modified implant surfaces show different biofilm compositions under *in vivo* conditions. *Clin Oral Implants Res* 2009;20:817-26.
 72. Jansson L, Ehnevid H, Lindskog S, Blomlöf L. Proximal restorations and periodontal status. *J Clin Periodontol* 1994;21:577-82.
 73. Jansson L, Blomster S, Forsgårdh A, Bergman E, Berglund E, Foss L, *et al.* Interactory effect between marginal plaque and subgingival proximal restorations on periodontal pocket depth. *Swed Dent J* 1997;21:77-83.
 74. Cenci MS, Lund RG, Pereira CL, de Carvalho RM, Demarco FF. *In vivo* and *in vitro* evaluation of Class II composite resin restorations with different matrix systems. *J Adhes Dent* 2006;8:127-32.
 75. Beyth N, Bahir R, Matalon S, Domb AJ, Weiss EI. Streptococcus mutans biofilm changes surface-topography of resin composites. *Dent Mater* 2008;24:732-6.
 76. Carvalho RM, Pereira JC, Yoshiyama M, Pashley DH. A review of polymerization contraction: the influence of stress development versus stress relief. *Oper Dent* 1996;21:17-24.
 77. Collins CJ, Bryant RW, Hodge KL. A clinical evaluation of posterior composite resin restorations: 8-year findings. *J Dent* 1998;26:311-7.
 78. Pashley DH. Clinical considerations of microleakage. *J Endod* 1990;16:70-7.
 79. Mitchell L. Decalcification during orthodontic treatment with fixed appliances – An overview. *Br J Orthod* 1992;19:199-205.
 80. Papaioannou W, Gizani S, Nassika M, Kontou E, Nakou M. Adhesion of Streptococcus mutans to different types of brackets. *Angle Orthod* 2007;77:1090-5.
 81. Busscher H, Weerkamp A. Specific and nonspecific interactions in bacterial adhesion to solid substrata. *FEMS Microbiol Rev* 1987;46:165-73.
 82. Busscher H, Sjollem J, van der Mei H. Relative importance of surface free energy as a measure of hydrophobicity in bacterial adhesion to solid surfaces. In: Doyle RJ, Rosenberg M, editors. *Microbial Cell Surface Hydrophobicity*. Washington, DC: American Society for Microbiology; 1990. p. 335-9.
 83. Van Loosdrecht M, Zehnder A. Energetics of bacterial adhesion. *Experientia* 1990;46:817-22.
 84. van Loosdrecht MC, Lyklema J, Norde W, Zehnder AJ. Influence of interfaces on microbial activity. *Microbiol Rev* 1990;54:75-87.
 85. Scheie A. Mechanisms of dental plaque formation. *Adv Dent Res* 1994;8:246-53.
 86. Bos R, van der Mei HC, Busscher HJ. Physico-chemistry of initial microbial adhesive interactions – Its mechanisms and methods for study. *FEMS Microbiol Rev* 1999;23:179-230.
 87. Teughels W, Van Assche N, Slipeen I, Quirynen M. Effect of material characteristics and/or surface topography on biofilm development. *Clin Oral Implants Res* 2006;17 Suppl 2:68-81.
 88. Kawai K, Urano M, Ebisu S. Effect of surface roughness of porcelain on adhesion of bacteria and their synthesizing glucans. *J Prosthet Dent* 2000;83:664-7.
 89. Patterson CJ, McLundie AC, Stirrups DR, Taylor WG. Efficacy of a porcelain refinishing system in restoring surface finish after grinding

Rashid: Effect of surface roughness on ceramics in dentistry

- with fine and extra-fine diamond burs. *J Prosthet Dent* 1992;68:402-6.
90. Hahn R, Weiger R, Netuschil L, Bruch M. Microbial accumulation and vitality on different restorative materials. *Dent Mater* 1993;9:312-6.
 91. Auschill TM, Arweiler NB, Brex M, Reich E, Sculean A, Netuschil L. The effect of dental restorative materials on dental biofilm. *Eur J Oral Sci* 2002;110:48-53.
 92. Scotti R, Kantorski KZ, Monaco C, Valandro LF, Ciocca L, Bottino MA. SEM evaluation of *in situ* early bacterial colonization on a Y-TZP ceramic: A pilot study. *Int J Prosthodont* 2007;20:419-22.
 93. Bremer F, Grade S, Kohorst P, Stiesch M. *In vivo* biofilm formation on different dental ceramics. *Quintessence Int* 2011;42:565-74.

Access this article online	
Quick Response Code: 	Website: www.eurjdent.com
Source of Support: Nil. Conflict of Interest: None declared	